




HPU2 Journal of Sciences: Natural Sciences and Technology

Journal homepage: <https://sj.hpu2.edu.vn>

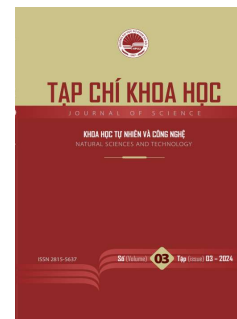

Article type: Research article

Stepwise grafting polyethyleneimine onto silica surface for Cu(II) removal

Mahmoud Elsayed Hafez^a, Thanh-Thuy Mai Thi^b, Van-Tuan Mai^c, Thuy-Tien Do^d, Thu-Huyen Dang Thi^d, Phuong-Uyen Pham^d, Hai-Yen Vu Thi^d, Quynh-Mai Le^d, The-Duyen Nguyen^{d*}

^aBeni-Suef University, Beni-Suef, Egypt

^bInstitute of Chemistry, Vietnam Academy of Science and Technology, Hanoi, Vietnam

^cElectric Power University, Hanoi, Vietnam

^dHanoi Pedagogical University 2, Vinh Phuc, Vietnam

Abstract

Polyethyleneimine (PEI) is a novel polymer that contains multiple amine groups that are suitable for chelation with many heavy metal ions (HMI). Anchoring PEI onto the surface of a solid substrate has been widely adopted to develop adsorbent materials with the hope of combining the HMI chelating ability of PEI with the heterogeneity of the substrate. Herein, the preparation of PEI grafted SiO₂ (PEI/SiO₂) has been demonstrated by a stepwise method in which SiO₂ nanoparticles were functionalized with 3-glycidoxypropyltrimethoxysilane (KH560) followed by refluxing with PEI. The method could provide PEI/SiO₂ material with 23.4% of PEI by weight. Studying the adsorption properties of PEI/SiO₂ with Cu(II) revealed that the adsorption of Cu(II) ions on PEI/SiO₂ followed Langmuir and Dubinin-Radushkevich models and included both chemisorption and physisorption. The adsorption capacity was about 25.3-27.3 mg/g. The stepwise method demonstrated in this study may be adopted to fabricate PEI based materials for HMI removal.

Keywords: Polyethyleneimine, PEI, silica, clean water, adsorption

1. Introduction

Heavy metal ions (HMI), microorganisms, and organic compounds are the main pollutants in water. At the same time, organic and microorganism pollutants are biodegradable and can be removed by aerobic or anaerobic processes. Meanwhile, HMI are indestructible and have to be removed artificially. The presence of HMI in water arises from both industry and human activities, such as

* Corresponding author, E-mail: nguyentheduyen@hpu2.edu.vn


<https://doi.org/10.56764/hpu2.jos.2024.3.3.20-26>

Received date: 23-7-2024 ; Revised date: 03-10-2024 ; Accepted date: 22-10-2024

This is licensed under the CC BY-NC 4.0

plating, metal smelting, mining, and tanning industries [1]. Due to the toxic and non-biodegradable properties, the concentration of HMI has to be detected and controlled at a proper limit [2]. Copper is a typical example that its concentration in water needs to be controlled below 3 mg/L, although it is an essential element to the human body [3]. Today, there are four main strategies for HMI removal including adsorption, membrane, chemical, electric, and photocatalytic methods. Each method has distinct advantages and is used in different scenarios, depending on the targeted wastewater. Among the available methods, adsorption is advanced by low-costs, technical maturity, and environmentally friendly [1]. Adsorption removal of HMI is based on the physicochemical interactions between an adsorbent and HMI which could involve ion exchange, electrostatic attraction, complexation, and precipitation [4]. Therefore, adding functional groups that could form coordination linkages to HMI onto the surface of activated carbon or silica is a significant strategy to increase the removal capacity of the adsorbent with high efficiency [5], [6].

Silica is a conventional substrate that can be fabricated in different forms including nanoparticles and porous materials. Because native silica has inactive Si–O–Si groups and relatively active Si–OH groups on the surface the post-functionalization of silica relies on the reactions of the silanol groups. Conventionally, alkoxy silane containing the target functional group, e.g. H₂N-R-Si(OCH₃)₃, is refluxed with silica to perform a condensation reaction between the as-formed R-Si-OH and the surficial Si-OH [7], [8], equation (1)



Practically, due to the surface hindrance, the density of grafted functional groups is relatively low so the absorption of HMI onto the surface of adsorbent depends on the individual groups. Alternatively, grafting polymer chains that involve dense functional groups onto silica has emerged as an effective method to enhance the adsorption capacity of silica-based materials [6]. To this strategy, polyethyleneimine (PEI) has been used widely because it contains multiple amine groups in repeating (-NH_x-CH₂-CH₂-) units that could chelate to various HMI [6], [9]–[12]. Herein, we have demonstrated the preparation of PEI grafted silica (PEI/SiO₂) via a stepwise method using 3-glycidoxypropyltrimethoxysilane (KH560) as a surficial linker. Cu(II) was selected as a typical HMI to evaluate the adsorption properties of PEI/SiO₂.

The results revealed that the adsorption of Cu(II) onto PEI/SiO₂ involved both chemical and physical adsorption with an adsorption maximum of 27.2 mg/g according to the Langmuir adsorption isotherm.

2. Experimental section

2.1. Chemicals

Chemicals including PEI (99%, MW = 600 Dalton, Aladdin Chemicals), KH560 (97%, Aladdin Chemicals), silica particles (SiO₂, Macklin), copper sulfate pentahydrate (99.9%, Xilong), and HPLC grade solvents were purchased and used without purifications.

2.2. The stepwise synthesis of PEI/SiO₂

A three-neck flask containing 5 g of freshly oxidized SiO₂, 150 ml toluene, and 36 mmol of KH560 was connected to a Schlenk line system and a temperature-controlled heating stirrer. Under Ar (99.98) atmosphere, the mixture was refluxed for 24 hours. After that, the solid was filtrated and washed with

ethanol to remove unreacted KH560. The solid was dried at 60°C to obtain KH560 grafted SiO₂, which was then added to a flask containing 100 ml methylenechloride and 1 g of PEI. The mixture was refluxed for 6 hours, filtrated, and washed with ethanol to obtain PEI/SiO₂.

2.3. Characterizations

Thermogravimetric analysis (TG) was conducted on a Thermo Plus EV02 (Rigaku, Japan) while an FT/IR-4600 spectrometer (Jasco, Japan) was used to perform infrared spectra. A nova touch 4xl was used to conduct the nitrogen adsorption – desorption isotherm for PEI/SiO₂ at -196°C.

2.4. Batch adsorption

In each Erlenmeyer flask, 0.1 g of PEI/SiO₂ and 50 ml of Cu(II) solution having a concentration ranging from 10 to 90 mg/L was added, closed, and shaken at a speed of 140 cycles per minute for 6 hours. The mixture was filtered by a syringe filter having a pore size of 0.21 µm to remove the adsorbent. The concentration of Cu(II) before (C_0) and after adsorption (C_e) was determined by a UV-Vis absorption method that was described by D. Guspita [13]. The absorbance of samples at 615 nm (Abs) was carried out on a UV-2450 spectrometer (Shimadzu, Japan). The correlation between Abs and Cu(II) concentration (C) was determined to be as in equation (2) with an $R^2 = 0.9998$:

$$C = 1320.8 \times Abs - 36.334 \text{ (mg/L)} \quad (2)$$

Cu(II) adsorption quantity (q_e) was determined by equation (3):

$$q_e = \frac{50 \times 10^{-3} (C_0 - C_e)}{0.1} \text{ (mg/g)} \quad (3)$$

The adsorption of Cu(II) on PEI/SiO₂ was studied using different models including Langmuir (equation 4), Freundlich (equation 5), and Dubinin-Radushkevich (equation 6) [14].

$$\frac{C_e}{q_e} = \frac{1}{q_{max}} C_e + \frac{1}{q_{max} K} \quad (4)$$

$$\ln(q_e) = \frac{1}{n} \ln(C_e) + \ln(K_F) \quad (5)$$

$$\ln(q_e) = -\beta \varepsilon^2 + \ln(q_m); \varepsilon = RT \ln \left(1 + \frac{1}{C_e} \right) \quad (6)$$

In the above equations, q_{max} is the maximum adsorption capacity (mg/g); K is Langmuir isotherm constant (L/mg); K_F is Freundlich isotherm constant (mg/g); n is adsorption intensity; β is Dubinin-Radushkevich isotherm constant (mol²/kJ²); R is the gas constant (J/molK); and T is the temperature (K).

3. Results and discussion

3.1. The structural properties of PEI/SiO₂ material

The stepwise synthesis of PEI/SiO₂ is schematically illustrated in Figure 1. SiO₂ was oxidized by a piranha solution containing concentrated H₂SO₄ and H₂O₂ with a volumetric ratio of 7/3 at 80°C to increase the density of surficial silanol groups. Upon refluxing in toluene, the methoxy (-OCH₃) groups of KH560 were slowly hydrolysis to form silanol groups which condensed with the surficial silanol to graft KH560 onto the surface of SiO₂. The bearing oxiranyl group of KH560 reacted with an amine group of PEI to anchor PEI chains onto the surface of SiO₂. The grafting of KH560 and PEI on the surface of SiO₂ was validated by FTIR spectra shown in Figure 2a. Two characteristic absorption peaks

of SiO₂ are seen at 1060 and 800 cm⁻¹ which are assigned to Si-O-Si anti-symmetric stretching and Si-O bending vibrations, respectively [15]. Additionally, a broad absorption band around 3360 cm⁻¹ is due to the stretching of the O-H bond in adsorbed water or silanol groups. After KH560 grafting, an absorption shoulder appeared at 2800-3000 cm⁻¹, which is attributed to the stretching vibration of C-H bonds in the methylene groups of the KH560. In the IR spectrum of KH560/SiO₂ sample, the characteristic absorption peaks originating from the C-O-C bond were not observed in the 1000-1200 cm⁻¹ region because they were likely overlapped by the vibrational absorption of Si-O-Si bonds. The existence of PEI in PEI/SiO₂ was confirmed by two characteristic peaks at 1640 and 1475 cm⁻¹, which are attributed to the bending vibration of N-H bonds in secondary amine groups and the stretching vibration of N-H bonds in primary amine groups, respectively [16], [17].

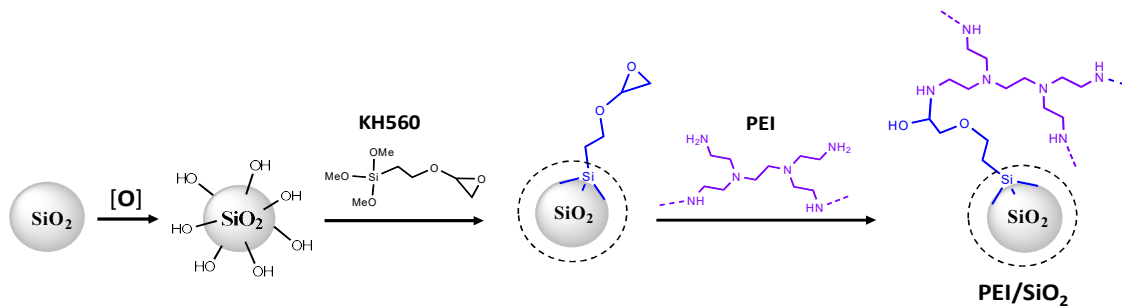


Figure 1. The stepwise synthesis of PEI grafted silica (PEI/SiO₂).

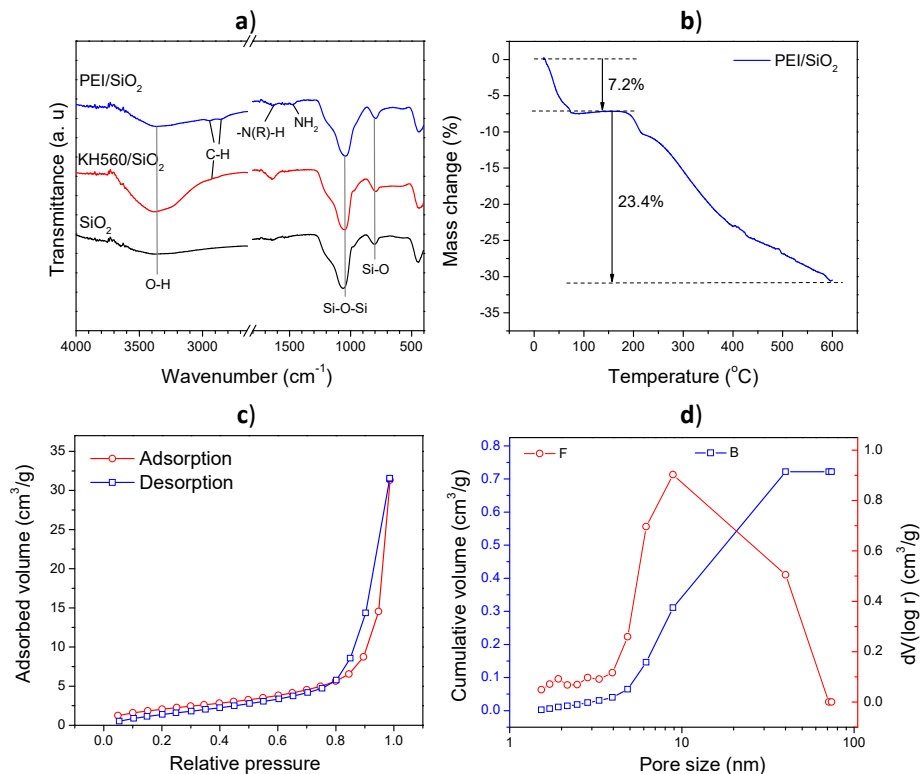


Figure 2. a) FTIR spectrum of PEI/SiO₂ in comparison with SiO₂ and KH560 grafted SiO₂ (KH560/SiO₂); b) TGA curve of PEI/SiO₂ in air conditions; c) nitrogen adsorption – desorption isotherm of PEI/SiO₂; d) pore size distribution of PEI/SiO₂.

TGA curve of PEI/SiO₂ conducted in air conditions, Figure 2b, involves two distinct mass-losing regions. The first mass loss at 80°C could be attributed to the desorption of water. After this temperature, PEI/SiO₂ is stable to about 200°C. At higher temperatures, the mass decreased gradually according to the thermal decomposition of organic components, which accounted for 23.4% by the mass of PEI/SiO₂. It is reasonable to take this value as the mass component of PEI in PEI/SiO₂.

3.2. The adsorption of Cu(II) ions on PEI/SiO₂ material

Nitrogen adsorption-desorption isotherm of PEI/SiO₂ shown in Figure 2c could be classified as an H3 type isotherm that has a narrow hysteresis loop and fast gradient changing in adsorption or desorption at high relative pressure [18]. Based on the adsorption data, the Brunauer-Emmett-Teller (BET) surface area of PEI/SiO₂ was determined to be 6.9 m²/g, which is comparable to silica nanoparticles [17]. Pore size distribution according to the Barrett-Joyner-Halenda (BJH) method of PEI/SiO₂ is shown in Figure 2d. The total volume of PEI/SiO₂ was about 0.72 cm³/g. Pores in PEI/SiO₂ were mesopores with a diameter ranging from 4 to 70 nm whereas pores of ~9 nm mostly accounted for the volume of PEI/SiO₂.

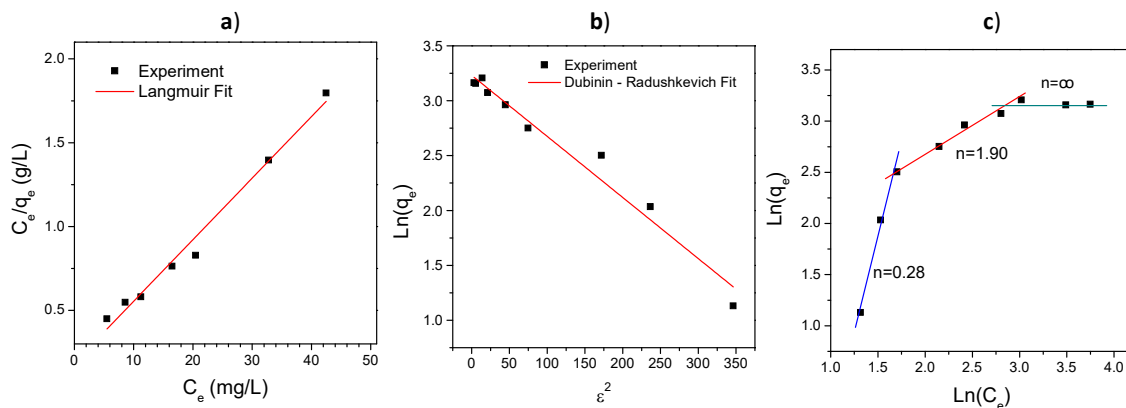


Figure 3. Fitting the Cu(II) adsorption of PEI/SiO₂ using different models: **a)** Langmuir, **b)** Dubinin – Radushkevich, and **c)** Freundlich.

To evaluate the HMI adsorption capability of the PEI/SiO₂ we used Cu(II) as an HMI model and the adsorption results were summarized in Figure 3. As shown in Figure 3a, the experiment data was fairly fitted with the Langmuir adsorption isotherm according to equation (4) with an R^2 value of 0.983. Consequently, the maximum adsorption capacity was estimated to be 27.2 mg/g. Additionally, the adsorption data was also well fitted with the Dubinin-Radushkevich model (equation 6) with an R^2 value of 0.967. The corresponding adsorption capacity was determined to be 25.3 mg/g, which is very close to the Langmuir adsorption maximum. For comparison, the adsorption capacity of PEI/SiO₂ in this study is higher than that of 3-aminopropyltriethoxysilane (19.2 mg/g) [19] or triethylenetetramine (23.9 mg/g) [20] functionalized mesoporous silica SBA-15) but it is relatively lower than PEI functionalized wheat straw (48.6 mg/g) [21] or mesoporous silica KIT-6 (36.43 mg/g) [22]. As shown in Figure 3a the adsorption data was well fitted by the Langmuir model revealing that the adsorption of Cu(II) ions onto PEI/SiO₂ was limited to a monolayer [23]. In addition, the adsorption energy was Gaussian distribution because the adsorption data also followed the Dubinin-Radushkevich model [14]. To study the type of adsorption, we plotted in Figure 3c the dependence of $\ln(q_e)$ on $\ln(C_e)$ according to the Freundlich model. In a low-concentration regime, the Freundlich adsorption intensity was 0.28, which is smaller than 1, indicating that the adsorption of Cu(II) ions onto PEI/SiO₂ was a chemisorption. When the

concentration was in the range of 5.5 – 20 mg/L, the adsorption intensity ($n= 1.9$), which is greater than 1, indicates that the adsorption was physical adsorption [24]. At higher concentrations ($C_e > 20$ mg/L), the adsorption reached infinite. The concentration dependence of the adsorption shown in Figure 3c could be due to the coexistence of different amine groups in PEI. There are amine groups in close proximity that could chelate to Cu(II) to perform chemisorption. After chemisorption sites are occupied the remaining Cu(II) ions tend to interact with individual amine groups of PEI. This single amine – Cu(II) interaction is weaker than the multiple amine groups – Cu(II) chelation interaction so the adsorption of Cu(II) was a physisorption. Those interactions are schematically illustrated in Figure 4.

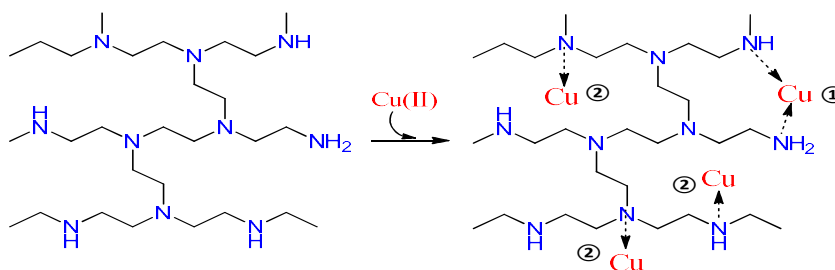


Figure 4. Representative chemisorption ① and physisorption ② of Cu(II) ions on PEI/SiO₂.

4. Conclusions

Polyethyleneimine (PEI) chains were grafted successfully on the surface of SiO₂ by a two-step procedure using KH560 as a linker. PEI was about 23.4% by mass in the final PEI/SiO₂ adsorbent. PEI/SiO₂ has mesopores whose diameter ranges from 3 to 70 nm with the accumulative volume of 0.72 cm³/g. By using Cu(II) as a model of heavy metal ions to study the adsorption properties of PEI/SiO₂, it has been demonstrated that the adsorbent has an adsorption capacity of 25.3-27.2 mg/g. The adsorption of Cu(II) ions onto PEI/SiO₂ followed Langmuir and Dubinin-Rudushkevich models and involved both chemisorption and physisorption. The stepwise preparation of PEI grafted SiO₂ demonstrated in this report could be adopted for the development of heavy metal ions adsorbents.

References

- [1] N. A. A. Qasem, R. H. Mohammed, and D. U. Lawal, "Removal of heavy metal ions from wastewater: A comprehensive and critical review," *Npj Clean Water*, vol. 4, no. 1, p. 36, Jul. 2021, doi: 10.1038/s41545-021-00127-0.
- [2] M. Balali-Mood, K. Naseri, Z. Tahergorabi, M. R. Khazdair, and M. Sadeghi, "Toxic mechanisms of five heavy metals: Mercury, lead, chromium, cadmium, and arsenic," *Front. Pharmacol.*, vol. 12, Apr. 2021, Art. No. 643972, doi: 10.3389/fphar.2021.643972.
- [3] D. J. Fitzgerald, "Safety guidelines for copper in water," *Am. J. Clin. Nutr.*, vol. 67, no. 5, pp. 1098S–1102S, May 1998, doi: 10.1093/ajcn/67.5.1098s.
- [4] A. Gul, A. Ma'amor, N. G. Khaligh, and N. Muhd Julkapli, "Recent advancements in the applications of activated carbon for the heavy metals and dyes removal," *Chem. Eng. Res. Des.*, vol. 186, pp. 276–299, Oct. 2022, doi: 10.1016/j.cherd.2022.07.051.
- [5] K. Gupta, P. Joshi, R. Gusain, and O. P. Khatri, "Recent advances in adsorptive removal of heavy metal and metalloid ions by metal oxide-based nanomaterials," *Coord. Chem. Rev.*, vol. 445, Oct. 2021, Art. no. 214100, doi: 10.1016/j.ccr.2021.214100.
- [6] Z. M. Ayalew, X. Guo, and X. Zhang, "Synthesis and application of polyethyleneimine (PEI)-based composite/nanocomposite material for heavy metals removal from wastewater: A critical review," *J. Hazard. Mater. Adv.*, vol. 8, Nov. 2022, Art. no. 100158, doi: 10.1016/j.hazadv.2022.100158.

- [7] P. Sharma, J. Prakash, and R. Kaushal, "Eco-friendly synthesis of amino and carboxyl-functionalized silica nanoparticles for enhanced adsorption of water pollutants," *Hybrid Adv.*, vol. 6, Aug. 2024, Art. no. 100209, doi: 10.1016/j.hybadv.2024.100209.
- [8] A. Alfawaz, A. Alsalmeh, A. Alkathiri, and A. Alswieleh, "Surface functionalization of mesoporous silica nanoparticles with brønsted acids as a catalyst for esterification reaction," *J. King Saud Univ. - Sci.*, vol. 34, no. 5, Jul. 2022, Art. no. 102106, doi: 10.1016/j.jksus.2022.102106.
- [9] J. Lan, B. Wang, and B. Gong, "Polyethyleneimine modified activated carbon for high-efficiency adsorption of copper ion from simulated wastewater," *Water Sci. Technol.*, vol. 86, no. 9, pp. 2465–2481, Nov. 2022, doi: 10.2166/wst.2022.345.
- [10] F. AN and B. GAO, "Chelating adsorption properties of PEI/SiO₂ for plumbum ion," *J. Hazard. Mater.*, vol. 145, no. 3, pp. 495–500, Jul. 2007, doi: 10.1016/j.jhazmat.2006.11.051.
- [11] W. Nowicki, "Structural studies of complexation of Cu(II) with aminosilane-modified silica surface in heterogeneous system in a wide range of pH," *Appl. Surf. Sci.*, vol. 469, pp. 566–572, Mar. 2019, doi: 10.1016/j.apsusc.2018.11.066.
- [12] O. Plohl, M. Finšgar, S. Gyergyek, U. Ajdnik, I. Ban, and L. F. Zemljič, "Efficient copper removal from an aqueous environment using a novel and hybrid nano-adsorbent based on derived-polyethyleneimine linked to silica magnetic nanocomposites," *Nanomaterials*, vol. 9, no. 2, Feb. 2019, Art. no. p. 209, doi: 10.3390/nano9020209.
- [13] D. Guspita and A. Ulianas, "Optimization of complex NH₃ with Cu²⁺ ions to determine levels of ammonia by UV-Vis spectrophotometer," *J. Phys. Conf. Ser.*, vol. 1481, no. 1, Mar. 2020, Art. no. 209, doi: 10.1088/1742-6596/1481/1/012040.
- [14] D. A.O, "Langmuir, Freundlich, Temkin and Dubinin-Radushkevich isotherms studies of equilibrium sorption of Zn²⁺ onto phosphoric acid modified rice husk," *IOSR J. Appl. Chem.*, vol. 3, no. 1, pp. 38–45, Jan. 2012, doi: 10.9790/5736-0313845.
- [15] L. Hu, Z. Pu, Y. Tian, X. Zheng, J. Cheng, and J. Zhong, "Preparation and properties of fluorinated silicon two-component polyurethane hydrophobic coatings," *Polym. Int.*, vol. 69, no. 5, pp. 448–456, Jan. 2020, doi: 10.1002/pi.5973.
- [16] H. Shi, J. Yang, Z. Ahmad, H. Zhang, and J. Chen, "Co-grafting of polyethyleneimine on mesocellular silica foam for highly efficient CO₂ capture," *Sep. Purif. Technol.*, vol. 325, Jul. 2023, Art. no. 124608, doi: 10.1016/j.seppur.2023.124608.
- [17] K. Choi *et al.*, "Chromium removal from aqueous solution by a PEI-silica nanocomposite," *Sci. Rep.*, vol. 8, Jan. 2018, Art. no. 1438, doi: 10.1038/s41598-018-20017-9.
- [18] K. Chen, T. Zhang, X. Chen, Y. He, and X. Liang, "Model construction of micro-pores in shale: A case study of Silurian Longmaxi Formation shale in Dianqianbei area, SW China," *Pet. Explor. Dev.*, vol. 45, no. 3, pp. 412–421, Jun. 2018, doi: 10.1016/S1876-3804(18)30046-6.
- [19] A. Shahbazi, H. Younesi, and A. Badii, "Functionalized SBA-15 mesoporous silica by melamine-based dendrimer amines for adsorptive characteristics of Pb(II), Cu(II) and Cd(II) heavy metal ions in batch and fixed bed column," *Chem. Eng. J.*, vol. 168, no. 2, pp. 505–518, Apr. 2011, doi: 10.1016/j.cej.2010.11.053.
- [20] J. I. Lachowicz *et al.*, "Adsorption of Cu²⁺ and Zn²⁺ on SBA-15 mesoporous silica functionalized with triethylenetetramine chelating agent," *J. Environ. Chem. Eng.*, vol. 7, no. 4, Aug. 2019, Art. no. 103205, doi: 10.1016/j.jece.2019.103205.
- [21] J. Dong, Y. Du, R. Duyu, Y. Shang, S. Zhang, and R. Han, "Adsorption of copper ion from solution by polyethyleneimine modified wheat straw," *Bioresour. Technol. Reports*, vol. 6, pp. 96–102, Jun. 2019, doi: 10.1016/j.biteb.2019.02.011.
- [22] J. Wei, S. Chen, Y. Li, Z. He, L. Geng, and L. Liao, "Aqueous Cu(II) ion adsorption by amino-functionalized mesoporous silica KIT-6," *RSC Adv.*, vol. 10, no. 35, pp. 20504–20514, Jan. 2020, doi: 10.1039/d0ra03051a.
- [23] D. Le and A. Chu, "Study on the adsorption L- and D- proline on MKN-MWCNT-P5000 carbon nanotubes from aqueous solutions," *HPU2. Nat. Sci. Tech.*, vol. 03, no. 02, pp. 50–58, Aug. 2024, doi: 10.56764/hpu2.jos.2024.3.2.50-58.
- [24] P. Senthil Kumar, S. Ramalingam, R. V. Abhinaya, K. V. Thiruvengadaravi, P. Baskaralingam, and S. Sivanesan, "Lead(II) adsorption onto sulphuric acid treated cashew nut shell," *Sep. Sci. Technol.*, vol. 46, no. 15, pp. 2436–2449, Oct. 2011, doi: 10.1080/01496395.2011.590174.